

Sandra G Gómez de Saravia and Silvia E Rastelli, Facultad de Ciencias Naturales y Museo (UNLP) and Marisa Viera, Facultad de Ciencias Exactas (UNLP), have conducted research into the use of natural compounds in paints to restrict algal growth. Here, Sandra G Gómez explains more

Natural compounds as additives in paints for controlling algal growth

Algae are a diverse group of photosynthetic organisms, ranging from microscopic single-cell micro-organisms to very large organisms, such as seaweed. Microalgae belonging to Chlorophyta (green algae) and Cyanophyta (blue-green algae) commonly occur in biofilms. In actual fact, these phototrophic biofilms are complex microbial communities formed by cyanobacteria, microalgae and heterotrophs¹ all embedded in a mucilaginous matrix of exopolysaccharides (EPS), mainly composed of polysaccharides ranging between 50–90%².

Phototrophic biofilms can produce an aesthetic effect and deterioration of a building's painted surfaces³. It is a common practice to treat these surfaces with mechanical brushes and/or biocides in order to eradicate the micro-organisms present. Several chemicals have been used for this purpose, such as acids, pyridines⁴, quaternary ammonium salts⁵ and organometallic compounds⁶. However, some of these products have been banned over time due to their associated environmental and health hazards⁷.

An alternative to those compounds, is the use of ecofriendly natural substances with known biocidal properties. The approach of using natural substances and herbs has been gaining prominence in the field of cultural heritage and conservation sciences since the 2000s⁸. Here we present the evaluation of the algacide properties of isoeugenol, vanillic acid and carvacrol incorporated in an acrylic waterborne paint formulation.

BIOASSAYS

Phototrophic biofilm developed on a painted external wall was scrapped (**Figure 1**). The sample was transported to the laboratory in a sterile condition and transferred to BG11 broth medium for maintenance of the algae community. Identification of the taxa to the genus level was based on the morphology of the individual cells, following microscopic examination and the use of literature data^{9,10}.

The algacide properties of three pure organic compounds (Sigma-Aldrich, USA) present in diverse plants were evaluated. **Table 1** shows some of their characteristics. The

micro-atmosphere test was used to evaluate the algacide activity of isoeugenol, vanillic acid and carvacrol¹¹. For this, 200µl of a seven day old algae culture containing 3.3 10⁶ algae ml⁻¹ was inoculated uniformly in a petri dish with BG11 agar. A sterile disk of filter paper (13mm) was placed on the centre of the inverted Petri dish lid and loaded with 50µl of the pure tested compound, or a dilution in DMSO from 125–1000mM (millimolar). The petri dishes were incubated under controlled photo period conditions (16/8hr light/darkness) and 25°C for 28 days. Growth control plates were made without filter paper and with filter paper moistened with DMSO to discard inhibition of the algal growth due to the solvent. All the tests were done in duplicate.

An exterior waterborne paint was formulated¹² and the compounds that exhibited algacide activity (isoeugenol and carvacrol) were incorporated separately into the base paint (2%w/w). The presence of the different compounds in the formulation was monitored by ATR FTIR using a Spectrum One spectrometer (Perkin Elmer, USA). The paints were applied by brushing on specimens of filter paper.

After applying three coats of paint, painted specimens were left to dry for seven days in a laboratory environment. Once dried, the samples were cut into squares (2.8cm side) for bioassays. Samples of painted filter paper were inoculated in spray form, with the phototrophic community given an initial number of approximately 1.4 10⁶ algae ml⁻¹. Then, three papers painted with the same type of paint were placed in petri dishes with BG11 agar and incubated under controlled conditions (16/8hr

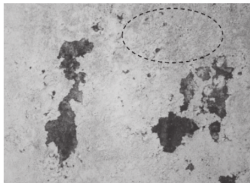


Figure 1. Painted wall with biodeterioration signs. The circle encloses the sampled zone




Compound and chemical structure	Characteristics
<p>Isoeugenol</p> 	It is a phenylpropene, a propenyl-substituted guaiacol. It is produced in the essential oils of plants, such as ylang-ylang (<i>Canangaodorata</i>). It can be synthesised from eugenol.
<p>Vanillic acid</p> 	It is an oxidised form of vanillin. It is also an intermediate in the production of vanillin from ferulic acid.
<p>Carvacrol</p> 	It is a monoterpene phenol. It is found in essential oils, such as oregano (<i>Origanummajorana</i>) and thyme (<i>Thymus vulgaris</i>).

Table 1. Characteristics of the natural organic compounds tested




Figure 2. Coccoids and filamentous microalgae present in the phototrophic biofilm




Figure 3. Results of the micro-atmosphere tests after 28 days of exposure to different concentrations of the natural compounds

light/darkness, 25°C) for 28 days. The test was performed in duplicate.

ALGAECIDE ACTIVITY

Observations with an optic microscope revealed that the biofilm is constituted by diverse genera of phototrophic organisms. The taxa determined belong to the Division Cyanophyta (*Xenococcaceae* spp., *Chroococcussp.* aff. *C. varius*, *Aphanocapsa* sp., *Pseudocapsa* sp. aff. *P. dubia*, *Aphanothece* sp., *Rhabdogloba* sp., *Leptolyngbya* sp. aff. *L. compacta*); Division Chlorophyta (*Chlorococcum* sp. aff. *Chlorella* sp., *Apatococcus lobatus*); and Division Streptophyta (*Klebsormidium* sp. aff. *K. fluitans*).

Organisms belonging to these taxa were reported in buildings in Latin America and in Europe⁹. Some of the phototrophic micro-organisms found in the sample are shown in Figure 2.

Figure 3 shows the results of the micro-atmosphere test at the end of experiment.

As it can be seen, carvacrol (250µM) and isoeugenol (250µM) showed an almost complete inhibition of the growth, while vanillic acid (even pure) was not effective in preventing the algal growth.

Taking into account the results of the micro-atmosphere tests, isoeugenol and carvacrol were incorporated into the waterborne paint. As it can be seen in Figure 4, the development of algal biomass only occurred in the control samples (paint without biocides). The growth of microalgae was completely inhibited by the addition of carvacrol or isoeugenol at 2%/w/w to the paint.

REMARKS

Carvacrol and isoeugenol showed good algaecide properties when incorporated to a paint formulation. In this way, they could be used in the formulation of environmental friendly exterior waterborne paints to avoid paint deterioration by algae.

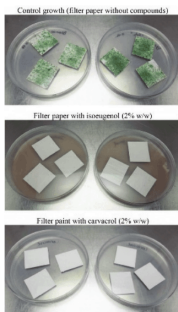


Figure 4. Results of the incubation of the filter papers painted with the control paint or paints with 2% of the natural compounds

Authors: Sandra G Gómez de Saravia, Silvia E Rastelli, Facultad de Ciencias Naturales y Museo (UNLP) and Marisa Viera, Facultad de Ciencias Exactas (UNLP), CIDEPIET (Centre of Research and Development in Paint Technology), Argentina
Email: s.gomez@cidepiet.gov.ar

Acknowledgements

This work was financed by grants from the National University of La Plata, Project 1V/1201, CONICET-PIP No 00314 and CICBA 195/17. The authors thank Dr G Blustein for the formulation of the exterior waterborne paint.

References

- Albertano P, 2012. 'Cyanobacterial biofilms in monuments and caves', *Whitton BA (Ed) Ecology of Cyanobacteria II: Their diversity in space and time*. Springer Science Business Media, pp317-344.
- Rossi F, Micheletti E, Bruno L, Adhikary S P, Albertano P, de Philipps R, 2012. 'Characteristics and role of the exocellular polysaccharides produced by five cyanobacteria isolated from phototrophic biofilms growing on stone monuments', *Biofouling* 28, pp215-224.
- Gaylarde P M, Gaylarde C C, 2007. 'Algae and cyanobacteria on painted buildings in Latin America', *International Biodegradation & Biodegradation* 46, pp93-97.
- Urzi C, De Leo F, 2007. 'Evaluation of the efficiency of water repellent and biocide compounds against microbial colonisation of mortars', *International Biodegradation & Biodegradation* 60, pp25-34.
- Diaz-Herraziz M, Jurado V, Cuezva S, Laiz L, Palecchi P, Tiano P, Sanchez-Moral S, Saiz-Jimenez C, 2013. 'The actinobacterial colonisation of Etruscan paintings', *Scientific Report* 3, pp1440-1445.
- Paulus W, 2004. *Directory of Microbiocides for the Protection of Materials - A Handbook*, Second ed. Kluwer Academic Publishers, Dordrecht.
- Veneranda M, Bianco-Zubiague R, Roselli G, Di Girolami G, Castro K, Madariaga J M, 2018. 'Evaluating the exploitability of several essential oils constituents as a novel biological treatment against cultural heritage biocolonisation', *Microchemical Journal* 138, pp1-6.
- Jeong S H, Lee H J, Kim D W, Chung Y J, 2018. 'New biocide for eco-friendly biofilm removal on outdoor stone monuments', *International Biodegradation & Biodegradation* 131, pp19-28.
- Komárek J, Anagnostidis K, 2000. 'Cyanoprokaryota Part 1 Chroococcales', *Ettli H, Gärtner G, Heynig H, Mollehufer (Eds) Süßwasserflora von Mitteleuropa* 19/1. G Fischer Jena, Stuttgart, Lübeck, Ulm p548.
- Komárek J, Anagnostidis K, 2005. 'Cyanoprokaryota Part 2 Oscillatoriales', *Büdel B, Krienitz L, Gärtner G, Schagerl M (Eds), Süßwasserflora von Mitteleuropa* 19/2. Elsevier, München, p759.
- DeleSPAUL G, de Billerbeck V G, Roques CG, Michel G, Marquis-Villuete C, Besièrre J M, 2000. 'The Antifungal Activity of Essential Oils as Determined by Different Screening Methods', *Journal of Essential Oil Research* 12, pp256-266.
- Gómez de Saravia S G, Rastelli S E, Blustein G, Viera M R, 2018. 'Natural compounds as potential algaecides for waterborne paints', *Journal of Coatings Technology and Research* 15, pp1191-1200.